

Stephen F. Austin State University

SFA ScholarWorks

Faculty Publications

Chemistry and Biochemistry

2010

Platinum and palladium complexes containing cationic ligands as catalysts for arene HID exchange and oxidation.

J. Brannon Gary

Stephen F Austin State University Department of Chemistry & Biochemistry, garyjb@sfasu.edu

Follow this and additional works at: https://scholarworks.sfasu.edu/chemistry_facultypubs

 Part of the [Chemistry Commons](#)

[Tell us](#) how this article helped you.

Repository Citation

Gary, J. Brannon, "Platinum and palladium complexes containing cationic ligands as catalysts for arene HID exchange and oxidation." (2010). *Faculty Publications*. 66.

https://scholarworks.sfasu.edu/chemistry_facultypubs/66


This Article is brought to you for free and open access by the Chemistry and Biochemistry at SFA ScholarWorks. It has been accepted for inclusion in Faculty Publications by an authorized administrator of SFA ScholarWorks. For more information, please contact cdsscholarworks@sfasu.edu.

C–H Activation

Platinum and Palladium Complexes Containing Cationic Ligands as Catalysts for Arene H/D Exchange and Oxidation**

Marion H. Emmert, J. Brannon Gary, Janette M. Villalobos, and Melanie S. Sanford*

The direct functionalization of C–H bonds has frequently been deemed a “Holy Grail” of organometallic chemistry.^[1] A seminal example of this transformation was the demonstration by Shilov and co-workers that platinum(II) salts catalyze the direct oxidation of alkanes into their corresponding alcohols and alkyl halides.^[2] Subsequent work in this area has focused on surveying diverse ligands for these reactions in an effort to enhance reactivity and selectivity, slow catalyst decomposition, and replace platinum(IV)-based oxidants with more cost-effective alternatives.^[3–5] In a key development, chemists at Catalytica identified [bpymPtCl₂] (bpym = bipyrimidine) as a pre-catalyst for the oxidation of CH₄ into CH₃OSO₃H in fuming H₂SO₄ (Scheme 1).^[5] The reaction

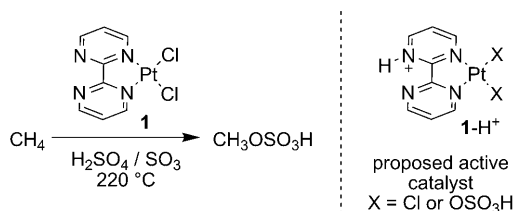


Scheme 1. Oxidative functionalization of methane with pre-catalyst **1**.

medium is believed to play several key roles in this system, including acting as a solvent, oxidant, and catalyst activator. Computational studies suggest that the active catalyst (**1-H**⁺) is formed by in-situ protonation of the ligand backbone, which limits oxidative catalyst degradation and renders the platinum center highly electrophilic and reactive for C–H bond cleavage.^[6]

Despite this initial success, it remains challenging to develop new generations of Group 10 metal catalysts that display higher turnover frequencies and operate in different, less corrosive media.^[3,4] A key goal of our efforts has been to identify ligands that mimic the desirable properties of protonated bipyrimidine but are stable in the absence of

strong acids.^[7] Herein, we describe the application of dicationic-bipyridine-based ligands in platinum- and palladium-catalyzed arene H/D exchange and oxidation reactions.

We considered dicationic ligands of general structure **2** (Scheme 2) for several key reasons. First, they contain

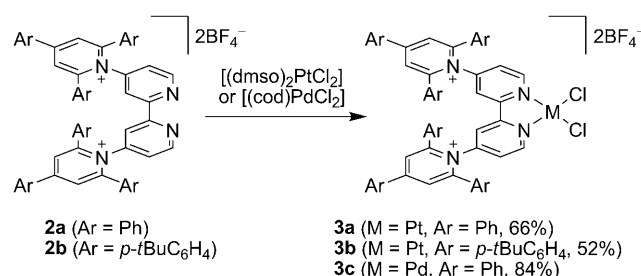

Scheme 2. Synthesis of platinum and palladium complexes **3 a–c**. cod = cycloocta-1,5-diene, dmsO = dimethyl sulfoxide.

electron-withdrawing quaternized nitrogen substituents, which should render coordinated metal centers highly electrophilic.^[8] Second, they are bidentate, sp² N-donors, which should allow a direct comparison with other bipyrimidine and bipyridine ligand systems. Third, the quaternized nitrogen atoms are not susceptible to decomposition by dealkylation or deprotonation, which has been problematic in related systems.^[5,7] Fourth, substituents can easily be added to the pyridinium ring to tune the solubility of these dications. Finally, ligands **2 a** and **2 b** are readily available in four steps from commercially available 2,2'-bipyridine (bpy) in 33 % and 24 % overall yield, respectively (for details, see the Supporting Information).^[9]

Platinum(II) complexes of **2 a** and **2 b** were synthesized by reaction of these ligands with [(dmsO)₂PtCl₂] in methanol at 60 °C to afford **3 a** and **3 b** in 66 % and 52 % yield, respectively, after recrystallization (Scheme 2). The analogous palladium(II) complex **3 c** was prepared in a similar fashion by the reaction of **2 a** with [(cod)PdCl₂] in dichloromethane at room temperature (84 % yield; Scheme 2). All of these complexes were fully characterized by ¹H, ¹³C, and ¹⁹F NMR spectroscopy and elemental analysis.

We first evaluated **3 a–c** as catalysts for H/D exchange^[10] between [D₄]acetic acid and benzene using an assay developed in our laboratory.^[10d] Under our standard conditions, (2 mol % [M], 4 mol % AgBF₄, 1 equiv C₆H₆ in 25 equiv of [D₄]AcOH, 150 °C), these complexes showed very high catalytic activity, with turnover frequencies (TOFs) of 0.1 s⁻¹ (**3 a,b**) and 0.05 s⁻¹ (**3 c**) after 15 minutes at 150 °C. For comparison, [dtbpyPtCl₂] (dtbpy = 4,4'-di-*tert*-butylbipyridine)

[*] Dr. M. H. Emmert, J. B. Gary, Dr. J. M. Villalobos, Prof. M. S. Sanford
Department of Chemistry, University of Michigan
930 N. University Ave, Ann Arbor, MI 48109 (USA)
Fax: (+1) 734-647-4865
E-mail: mssanford@umich.edu

[**] We thank the NSF for support of this work through the Center for Enabling New Technologies through Catalysis. M.H.E. thanks the DFG (German Research Council) for a postdoctoral fellowship (EM 219/1-1). J.B.G. thanks the NSF for a predoctoral fellowship.

Supporting information for this article is available on the WWW under <http://dx.doi.org/10.1002/anie.201002351>.

idine), [dtbpyPdCl₂], and bipyrimidine catalyst **1** provided TOFs of 0.0002, 0.002, and 0.003 s⁻¹, respectively, under identical conditions.^[10d] The catalysts were also compared on the basis of turnover numbers (TONs). Complexes **3a–c** achieved the statistical maximum TON of 242 after 24 hours,^[11,12] which is also superior to the results with [dtbpyPtCl₂], [dtbpyPdCl₂], and **1** (TON = 144 ± 12, 90 ± 18, and 94 ± 13 under analogous conditions).^[10d] Lowering the catalyst loading of **3a** to 0.1 mol% resulted in turnovers of 3273 ± 110 after 48 hours at 150 °C, which demonstrates the high activity and stability of this species, even upon prolonged heating at elevated temperatures. Finally, we decreased the reaction temperature to 100 °C. As shown in Figure 1, [dtbpyPtCl₂], [dtbpyPdCl₂], and **1** promoted very little H/D exchange under these conditions, whilst **3a–c** maintained high activity.

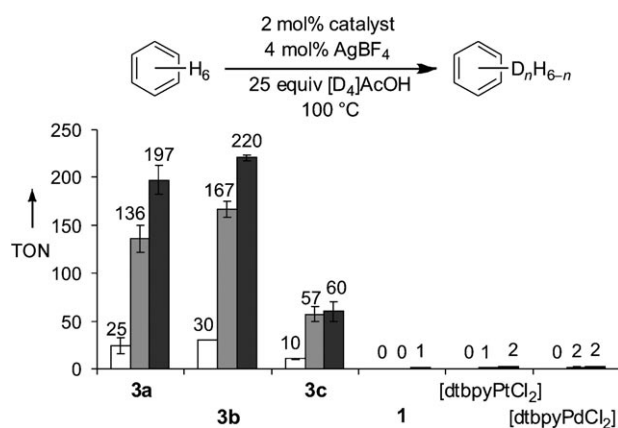


Figure 1. Turnover numbers for H/D exchange between benzene and [D₄]AcOH at 100 °C, catalyzed by **1**, **3a–c**, [dtbpyPtCl₂], and [dtbpyPdCl₂] after 2 h (white), 24 h (light gray), and 48 h (dark gray). Conditions: catalyst (2 mol%, 5 μmol), benzene (22.3 μL, 0.250 mmol), AgBF₄ (1.9 mg, 10 μmol), [D₄]AcOH (0.37 mL, 6.5 mmol, 25 equiv relative to benzene).

There are two possible explanations for the high H/D exchange activity of **3a–c**. The first is that the cationic ligands enhance the reactivity of the coordinated metal center towards arene C–H cleavage to generate metal σ-aryl intermediates (through an organometallic mechanism). An alternative possibility is that the Lewis acidic metal centers promote proton catalysis through an electrophilic aromatic substitution (Ar–S_E) pathway. To gain insight into the mechanism for H/D exchange, we examined the site-selectivity of D incorporation with catalyst **3a** for a variety of substituted arenes at partial (ca. 25%) conversion. Table 1 compares the observed selectivity (as determined by ¹H NMR spectroscopy) to the product ratio for electrophilic bromination^[13,14] (Table 1, entries 1–3); furthermore, the selectivity of DCl/CF₃CO₂D-catalyzed H/D exchange with bromobenzene is shown in entry 4. In all cases, the site selectivity with **3a** differed dramatically from that observed in Ar–S_E. This is strongly suggestive of an organometallic pathway for the platinum/palladium-catalyzed H/D exchange reactions.

Table 1: Comparison of site-selectivity for arene H/D exchange^[a,b] at 25% conversion with site-selectivity obtained in electrophilic aromatic bromination.

Entry	R	H/D exchange <i>ortho/meta/para</i> (catalyst)	Ar–S _E <i>ortho/meta/para</i>
1	Et	1.70:1.33:1 (3a) ^[a]	1.72:0.06:1 ^[c]
2	CO ₂ Et	1.26:2:1.33 (3a) ^[a]	0:2:0 ^[d]
3	Br	2.92:1.19:1 (3a) ^[a]	0.48:0.01:1 ^[c]
4	Br	1.15:0.28:1 (DCl/THF) ^[b]	0.48:0.01:1 ^[c]

[a] Conditions: **3a** (3.0 mg, 2.5 μmol, 0.5 mol%), AgBF₄ (1.9 mg, 5.0 μmol, 1.0 mol%), RPh (0.50 mmol, 1.0 equiv), [D₄]AcOH (0.71 mL, 25 equiv), 150 °C. [b] Conditions: BrPh (26.3 μL, 39.3 mg, 0.250 mmol, 1.00 equiv), [D₁]TFA (0.51 mL, 0.719 g, 6.25 mmol, 25.0 equiv), DCl in D₂O (35%, 0.05 mL), 38 h, 150 °C. [c] See Ref. [13]. [d] See Ref. [14]. TFA = trifluoroacetic acid, THF = tetrahydrofuran.

The substrate scope of H/D exchange reactions catalyzed by **3a** was also investigated. As summarized in Figure 2, naphthalene, veratrole, 1,2-dichlorobenzene, bromobenzene, ethylbenzoate, (H₃C)₃CCH₂Ph, *sec*-butylbenzene, cumene,

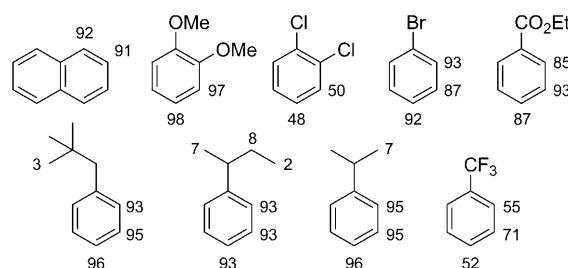


Figure 2. Substrate scope of H/D exchange catalyzed by **3a**; numbers in small font are %D incorporation. Conditions: **3a** (3.0 mg, 2.5 μmol, 2.0 mol%), substrate (0.125 mmol, 1.00 equiv), AgOTf (5.0 μmol, 4.0 mol%), [D₄]AcOH (0.36 mL, 0.40 g, 6.25 mmol, 50 equiv), 48 h (naphthalene, veratrole, PhBr) or 168 h (other substrates). Tf = trifluoromethanesulfonyl.

and trifluorotoluene all underwent extensive (48–98%) aromatic H/D exchange with CD₃CO₂D. Significant (2–8%) deuteration was also observed at unactivated sp³ C–H sites along the alkyl chains. In an interesting contrast, substrates that do not bear a tethered aromatic group (e.g. cyclooctane, 2,2,3,3-tetramethylbutane, and methane) did not show H/D exchange reactivity with catalyst **3a** under analogous conditions. This observation suggests that the arene moiety plays a role in directing the catalyst to the unactivated sp³ sites, likely via cyclometalation^[15] or π-coordination.^[16] The observation of aliphatic H/D exchange provides further evidence to support an organometallic mechanism, as this side reaction is expected to be negligible under proton catalysis.

The H/D-exchange experiments probed the reactivity of **3a–c** in C–H bond cleavage, which is only the first step of a

potential C–H functionalization process. Thus, it was important to determine whether the high reactivity and stability of these new complexes for arene H/D exchange correlated to catalytic activity in arene oxidation. To test this, we conducted preliminary studies of the effect of ligand **2a** on the Pd(OAc)₂-catalyzed acetoxylation of arenes with PhI(OAc)₂.^[17,18] As illustrated in Figure 3, the use of Pd(OAc)₂/

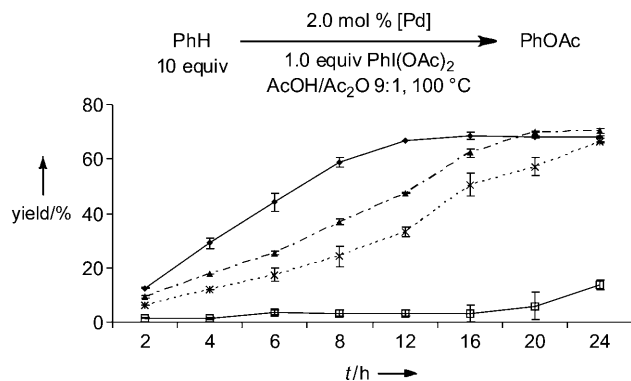


Figure 3. Pd^{II} catalyzed acetoxylation of benzene. Catalysts [Pd]: (◆) Pd(OAc)₂/**2a** 2:1; (☆) Pd(OAc)₂/bpy (2:1); (×) Pd(OAc)₂; (□) Pd(OAc)₂/bpym (2:1).

2a for the oxidation of benzene resulted in a significantly enhanced reaction rate compared to the best catalysts reported to date for this transformation (Pd(OAc)₂^[17] or Pd(OAc)₂/bpy 2:1^[18]). Similarly enhanced turnover frequencies were obtained in the C–H acetoxylation of naphthalene, 1,2-dichlorobenzene, chlorobenzene, bromobenzene, ethylbenzoate, and α,α,α -trifluorotoluene using Pd(OAc)₂/**2a** (for full details, see the Supporting Information). These initial results show that ligand **2a** can be used to generate robust, highly active palladium C–H oxidation catalysts.

In conclusion, the application of cationic pyridinium substituted ligands of general structure **2** for Group 10 C–H functionalization catalysis has been described. Both platinum and palladium complexes of these ligands display high catalytic activity for arene H/D exchange; furthermore, the combination of Pd(OAc)₂/**2a** shows enhanced activity for arene acetoxylation, compared with the best previously reported catalysts.^[17,18] Further applications of late transition metal complexes of **2a** and **2b** in C–H functionalization reactions are currently underway in our laboratory.

Received: April 20, 2010
 Revised: June 1, 2010
 Published online: July 15, 2010

Keywords: C–H activation · H/D exchange · ligand design · oxidation · platinum

- [1] B. A. Arndtsen, R. G. Bergman, T. A. Mobley, T. H. Peterson, *Acc. Chem. Res.* **1995**, *28*, 154–162.
- [2] a) N. F. Goldshleger, V. V. Eskova, A. E. Shilov, A. A. Shteinmann, *Zh. Fiz. Khim.* **1972**, *46*, 1353–1364; b) A. E. Shilov, G. B. Shulpin, *Chem. Rev.* **1997**, *97*, 2879–2932.
- [3] A. F. Heyduk, H. A. Zhong, J. A. Labinger, J. E. Bercaw, *Activation and Functionalization of C–H Bonds*, ACS Symp. Ser. **2004**, *885*, pp. 250–264.
- [4] For examples, see: a) M. Muehlhofer, T. Strassner, W. A. Herrmann, *Angew. Chem.* **2002**, *114*, 1817–1819; *Angew. Chem. Int. Ed.* **2002**, *41*, 1745–1747; b) I. Bar-Nahum, A. M. Khenkin, R. Neumann, *J. Am. Chem. Soc.* **2004**, *126*, 10236–10237; c) D. Meyer, M. A. Taige, A. Zeller, K. Hohlfeld, S. Ahrens, T. Strassner, *Organometallics* **2009**, *28*, 2142–2149; d) G. S. Chen, J. A. Labinger, J. E. Bercaw, *Organometallics* **2009**, *28*, 4899–4901; e) R. Palkovits, M. Antonietti, P. Kuhn, A. Thomas, F. Schüth, *Angew. Chem.* **2009**, *121*, 7042–7045; *Angew. Chem. Int. Ed.* **2009**, *48*, 6909–6912; f) J. E. Kreutz, A. Shukhaev, W. Du, S. Druskin, O. Daugulis, R. F. Ismagilov, *J. Am. Chem. Soc.* **2010**, *132*, 3128–3132.
- [5] R. A. Periana, D. J. Taube, S. Gamble, H. Taube, T. Satoh, H. Fujii, *Science* **1998**, *280*, 560–564.
- [6] a) J. Kua, X. Xu, R. A. Periana, W. A. Goddard, *Organometallics* **2002**, *21*, 511–525; b) X. Xu, J. Kua, R. A. Periana, W. A. Goddard, *Organometallics* **2003**, *22*, 2057–2068; c) A. Paul, C. B. Musgrave, *Organometallics* **2007**, *26*, 793–809; d) M. Ahlquist, R. A. Periana, W. A. Goddard, *Chem. Commun.* **2009**, 2373–2373.
- [7] J. M. Villalobos, A. J. Hickman, M. S. Sanford, *Organometallics* **2010**, *29*, 257–262.
- [8] For example, the Hammett σ_{para} value for NMe₃⁺ is 0.96.
- [9] P. P. Lainé, I. Ciofini, P. Ochsenbein, E. Amouyal, C. Adamo, F. Bedioui, *Chem. Eur. J.* **2005**, *11*, 3711–3727; and the references therein.
- [10] For examples, see: a) K. J. H. Young, S. K. Meier, J. M. Gonzales, J. Oxgaard, W. A. Goddard, R. A. Periana, *Organometallics* **2006**, *25*, 4734–4737; b) V. R. Ziatdinov, J. Oxgaard, O. A. Mironov, K. J. H. Young, W. A. Goddard, R. A. Periana, *J. Am. Chem. Soc.* **2006**, *128*, 7404–7405; c) G. Gerdes, P. Chen, *Organometallics* **2004**, *23*, 3031–3036; d) A. J. Hickman, J. M. Villalobos, M. S. Sanford, *Organometallics* **2009**, *28*, 5316–5322.
- [11] All reported TONs and TOFs are corrected for the background H/D exchange reaction of AgCl, which is formed as a by-product under the reaction conditions.
- [12] For TONs obtained after 2 h and 24 h at 2, 1, 0.5, 0.25, and 0.1 mol % catalyst loading (**3a**), see the Supporting Information.
- [13] H. Gilow, *J. Chem. Educ.* **1977**, *54*, 450–452.
- [14] S. Rozen, M. Brand, *J. Chem. Soc. Chem. Commun.* **1987**, 752–753.
- [15] T. G. Driver, M. W. Day, J. A. Labinger, J. E. Bercaw, *Organometallics* **2005**, *24*, 3644–3654.
- [16] N. Ito, H. Esaki, T. Maesawa, E. Imamiya, T. Maegawa, H. Sajiki, *Bull. Chem. Soc. Jpn.* **2008**, *81*, 278–286.
- [17] T. Yoneyama, R. H. Crabtree, *J. Mol. Catal. A* **1996**, *108*, 35–40.
- [18] a) L. Ebersson, L. Jönsson, *J. Chem. Soc. Chem. Commun.* **1974**, 885–886; b) L. Ebersson, L. Jönsson, *Acta Chem. Scand. Ser. B* **1976**, *30*, 361–364.